

Provided for non-commercial research and education use.  
Not for reproduction, distribution or commercial use.



This article appeared in a journal published by Elsevier. The attached copy is furnished to the author for internal non-commercial research and education use, including for instruction at the authors institution and sharing with colleagues.

Other uses, including reproduction and distribution, or selling or licensing copies, or posting to personal, institutional or third party websites are prohibited.

In most cases authors are permitted to post their version of the article (e.g. in Word or Tex form) to their personal website or institutional repository. Authors requiring further information regarding Elsevier's archiving and manuscript policies are encouraged to visit:

<http://www.elsevier.com/authorsrights>



Contents lists available at ScienceDirect

Journal of Power Sources

journal homepage: [www.elsevier.com/locate/jpowsour](http://www.elsevier.com/locate/jpowsour)

# Significant impact on cathode performance of lithium-ion batteries by precisely controlled metal oxide nanocoatings via atomic layer deposition



Xifei Li<sup>a</sup>, Jian Liu<sup>a</sup>, Xiangbo Meng<sup>a</sup>, Yongji Tang<sup>a</sup>, Mohammad Norouzi Banis<sup>a</sup>, Jinli Yang<sup>a</sup>, Yuhai Hu<sup>a</sup>, Ruying Li<sup>a</sup>, Mei Cai<sup>b</sup>, Xueliang Sun<sup>a,\*</sup>


<sup>a</sup> Nanomaterials and Energy Lab, Department of Mechanical and Materials Engineering, University of Western Ontario, London, Ontario N6A 5B9, Canada

<sup>b</sup> General Motors R&D Center, Warren, MI 48090-9055, USA

## HIGHLIGHTS

- ALD derived metal oxide (TiO<sub>2</sub>, ZrO<sub>2</sub>, Al<sub>2</sub>O<sub>3</sub>) coatings were successfully performed.
- Coatings could significantly increase battery performance of the commercial LiCoO<sub>2</sub>.
- Al<sub>2</sub>O<sub>3</sub> coating brings the best cycling stability.
- ZrO<sub>2</sub> coating contributes to the best rate capability.

## GRAPHICAL ABSTRACT

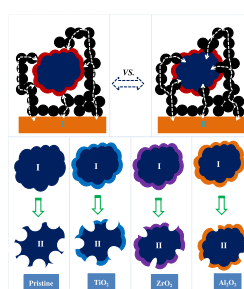

## ARTICLE INFO

### Article history:

Received 29 May 2013

Received in revised form

8 August 2013

Accepted 16 August 2013

Available online 29 August 2013

### Keywords:

LiCoO<sub>2</sub> cathode  
Atomic layer deposition  
Metal oxide coatings  
Lithium ion batteries  
Cobalt dissolution

## ABSTRACT

LiCoO<sub>2</sub> in the commercial lithium ion batteries has been suffering from its poor cycling performance at high cutoff voltages. In this study, we employ an atomic layer deposition (ALD) technique to surface-modify a LiCoO<sub>2</sub> material with various thickness-controlled metal oxide (TiO<sub>2</sub>, ZrO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub>) coatings to improve its battery performance. The effects of the metal oxide coatings on the electrochemical performance of LiCoO<sub>2</sub> electrode are studied in detail. It is demonstrated that a uniform and dense coating via the ALD route on LiCoO<sub>2</sub> powder can lower the battery performance due to an obvious decrease in lithium diffusion and electron transport with the coating layers. In contrast, it is revealed that a direct coating on prefabricated LiCoO<sub>2</sub> electrodes performs much better than a coating on LiCoO<sub>2</sub> powders. It is further disclosed that the improved electrochemical performance of coated LiCoO<sub>2</sub> electrode is highly dependent on the coating materials. Of the three coating materials, the Al<sub>2</sub>O<sub>3</sub> coating results in the best cycling stability while the ZrO<sub>2</sub> coating contributes to the best rate capability. It is thus suggested that the coating materials are functionally specific, and for the best improvement of a cathode, a particular coating material should be sought.

Crown Copyright © 2013 Published by Elsevier B.V. All rights reserved.

## 1. Introduction


Various lithium transition metal oxides (such as LiCoO<sub>2</sub>, LiNiO<sub>2</sub>, LiCo<sub>x</sub>Ni<sub>1-x</sub>O<sub>2</sub>, LiMn<sub>2</sub>O<sub>4</sub>, LiFe(Mn)PO<sub>4</sub>, LiNi<sub>1/3</sub>Mn<sub>1/3</sub>Co<sub>1/3</sub>O<sub>2</sub>, etc) have

been successfully employed as cathodes in rechargeable lithium ion batteries (RLIBs) since the first commercialized RLIBs by SONY in 1991 [1–3]. LiCoO<sub>2</sub>, proposed by Goodenough et al. in 1980, [4] is the first commercialized cathode material in RLIBs [5,6], and has been considered as one of the most attractive cathodes due to its ease of production and superior battery performance including high energy density and high working potential (~3.9 V vs. Li/Li<sup>+</sup> couple) [7–9]. As an important cathode in RLIBs, the α-NaFeO<sub>2</sub>

\* Corresponding author. Tel.: +1 519 661 2111x87759; fax: +1 519 661 3020.  
E-mail address: [xsun@eng.uwo.ca](mailto:xsun@eng.uwo.ca) (X. Sun).

layer-structured LiCoO<sub>2</sub> (space group-R3m,  $a = 2.815\text{--}2.816 \text{ \AA}$ ,  $c = 14.05\text{--}14.08 \text{ \AA}$ ) with oxygen in a cubic close-packed arrangement is composed of consecutively arranged Li<sup>+</sup> and Co<sup>3+</sup> ions. Moreover, octahedral LiO<sub>6</sub> and CoO<sub>6</sub> share common edges between the layers in the unit cell of LiCoO<sub>2</sub> [7,10,11]. To reduce the cathode material size into the nanoscale is an important approach to increase cycling performance [9,12–17]. For example, nanostructured LiCoO<sub>2</sub> cathodes (representatively including nanoparticles [16], nanowires [17], and nanosheets [9], etc.) provide shortened diffusion pathway for lithium ion insertion/extraction and electron transport. In addition, the increased surface-to-volume ratio of nanostructured LiCoO<sub>2</sub> facilitates lithium ion accessibility from the electrolyte with higher efficiency over bulk LiCoO<sub>2</sub> [18]. However, the larger surface area of nanostructured LiCoO<sub>2</sub> often results in a heavier formation of solid electrolyte interphase (SEI) in comparison to its bulk counterparts. As a result, nanostructured LiCoO<sub>2</sub> is inevitably accompanied by the production of more heat [19]. In addition, a thicker SEI layer leads to deteriorated rate capabilities at high rates, due to its low electrical conductivity as a lithium-ion barrier [20]. Even worse, nanostructured LiCoO<sub>2</sub> suffers from its poor tap density, leading to the low RLIB energy density. In contrast, micron-sized LiCoO<sub>2</sub> cathode mitigates somewhat the above-discussed challenges, and shows more practical in commercial RLIBs. But, how to further increase battery performance of micron-sized LiCoO<sub>2</sub> cathode has been a crucial challenge in the RLIB development.

LiCoO<sub>2</sub> cathode exhibits a theoretical capacity of 272 mAh g<sup>-1</sup>. However, when the battery is charged a cutoff voltage up to 4.2 V, only half lithium is extracted from LiCoO<sub>2</sub> to Li<sub>0.5</sub>CoO<sub>2</sub>, resulting in the limited capacity (only ~140 mAh g<sup>-1</sup>) in practical applications [21]. Thus, it is a well accepted strategy to charge LiCoO<sub>2</sub> cathode beyond 4.2 V, in order to utilize more lithium ions from the cathode and to increase the specific capacity and the energy density of LiCoO<sub>2</sub> [22,23]. However, previous studies also revealed that the inevitable moisture in the RLIB electrolyte could induce LiPF<sub>6</sub> decomposition and form HF acid, described as following [24]:



The formed HF acid aggravates the dissolution of LiCoO<sub>2</sub> cathode, moreover, the charge cutoff voltage over 4.2 V incurs the dissolution of LiCoO<sub>2</sub> into the electrolyte, thereby causing an increased capacity fade upon cycling [23,25,26]. In this context, it is critical to mitigate the capacity fading of LiCoO<sub>2</sub> in order to satisfy RLIB application.

The charge–discharge cycling of RLIB cathodes is highly related with their surface chemistry [27], thus surface modification via coating was demonstrated being an effective strategy to decrease the cathode dissolution. To date, many metal oxides (such as TiO<sub>2</sub>, ZrO<sub>2</sub>, and Al<sub>2</sub>O<sub>3</sub> et al.) were successfully reported as surface coatings [28–34]. Their functional roles may present in preventing the cathode materials from their direct contact with the electrolyte, simultaneously maintaining ionic conduction pathways, suppressing the release of oxygen and the phase transition, and decreasing the disorder of cations in crystal sites [35,36]. For example, a mechanothermal process was applied to coat TiO<sub>2</sub> on LiCoO<sub>2</sub> cathode to obtain higher cycling performance [28]. The ZrO<sub>2</sub> coated LiCoO<sub>2</sub> showed better battery performance than the pristine one at both room temperature and elevated temperature of 55 °C [30]. It was found that the ultra-thin Al<sub>2</sub>O<sub>3</sub> coating on LiCoO<sub>2</sub> resulted in 250% improvement in reversible capacity in comparison to the bare

one [32]. Of three reported different configurations of surface coating, i.e., rough coating, core–shell structure coating and ultra-thin film coating [34], the first one cannot fully coat a cathode material, and the intact area leaves the cathode vulnerable to the reactions with the electrolyte. In comparison, the second choice is successful in fully coating a cathode. Unfortunately, the resultant coatings are often very thick and thereby impede the transport of lithium and electron. Therefore, the ultra-thin film coating as the third choice is commonly regarded as the most promising approach, due to its pinhole-free films with complete protection from the electrolyte [34]. To fulfill last route, recently atomic layer deposition (ALD) is receiving an increasing attention ascribed to its unique capabilities in depositing controllable atomic-level thin films with high quality. A lot of efforts have been focused on ALD-coatings onto cathodes [33,37–42], anodes [43–45], and separator [46] to increase electrochemical performance of RLIBs. In case of deposition of metal oxides, ALD has numerous reports including Al<sub>2</sub>O<sub>3</sub>, TiO<sub>2</sub>, and ZrO<sub>2</sub> etc. on various substrates [33,37–46]. To the best of our knowledge, however, a systematic study of various coating layers (Al<sub>2</sub>O<sub>3</sub>, TiO<sub>2</sub>, and ZrO<sub>2</sub>) on the electrodes, in particular from the point of view of electrochemical characterization, is scarce.

In this study, we conducted a systematic comparative investigation on the effects of three metal oxide coatings including TiO<sub>2</sub>, ZrO<sub>2</sub>, and Al<sub>2</sub>O<sub>3</sub> on the electrochemical performance of a commercial LiCoO<sub>2</sub> cathode material with micron-size. The controllable coatings were deposited via ALD. In addition, the effects due to coating thickness were also addressed in study. It was demonstrated that the controllable coatings are effective in improving both cycling stability and rate capability of LiCoO<sub>2</sub> cathode. More importantly, it was inspired from this study that ALD and its resultant materials may ultimately contribute more for robust and high-efficient RLIBs.

## 2. Experimental

### 2.1. Preparation of LiCoO<sub>2</sub> electrode

LiCoO<sub>2</sub> electrodes were prepared by slurry-casting on Al foils that served as current collectors. The slurry contained 80 wt% the cathode materials (commercial LiCoO<sub>2</sub> with the particle size of 3–10 μm, as shown in Fig. S1 in Supplementary data), 10 wt% carbon black and 10 wt% poly(vinylidene) fluoride binder in the *N*-methylpyrrolidinone (NMP) solvent. The obtained electrode was dried in a vacuum at 90 °C overnight.

### 2.2. Metal oxide coatings on LiCoO<sub>2</sub> electrode via ALD

Various metal oxides (TiO<sub>2</sub>, ZrO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub>) were directly coated on the LiCoO<sub>2</sub> electrode in an ALD reactor (Savannah 100, Cambridge Nanotechnology Inc., USA). Titanium tetrakisopropoxide (TTIP), tetrakis dimethylamido zirconium (Zr(NMe<sub>2</sub>)<sub>4</sub>) and Trimethylaluminum (TMA) were chose as Ti, Zr and Al precursor respectively, while H<sub>2</sub>O was used as the oxidizer in three cases. The deposition temperature was set as 85, 100 and 150 °C for TiO<sub>2</sub>, ZrO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub>, respectively. One ALD cycle was executed with the following six steps: (1) pulsing of the first precursor with  $t_1$  s; (2) a 3.0 s extended exposure of the first precursor to the cathode electrode; (3) purging of residual precursor and any byproducts with  $t_2$  s; (4) pulsing of the second precursor with  $t_3$  s; (5) a 3.0 s extended exposure of the second precursor to the cathode electrode; (6) purging of residual precursor and any byproducts with  $t_4$  s. The ALD sequence was expressed as  $t_1 - t_2 - t_3 - t_4$  in short. During an ALD process, the purging time is an important parameter, thus this parameter we used in this study was optimized. For example, as shown in Fig. S2, in a case of TiO<sub>2</sub> coated LiCoO<sub>2</sub>, when the purging time was set as 5 s,

many small particles can be clearly found due to precursor condensation on the cathode followed by a process of chemical vapor deposition (it is well worth noting that the marked particles were from small particles of commercial cathode or carbon black as conductive agent in the electrodes). To increase purging time to 10 s, the amount of small particles decreased, which indicates that the prolonged purging time could help decrease the precursor condensed on the LiCoO<sub>2</sub> cathode. Further prolonging purging time up to 20 s, as a result, few small particles were deposited during the ALD process. Therefore, in this study, the purging time was set as 20 s or longer. Longer purging time could weaken or avoid precursor condensation on the cathode. Therefore, the deposition of TiO<sub>2</sub>, ZrO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub> was performed by using sequence of 2 (TTIP) – 20 – 1 (H<sub>2</sub>O) – 20, 0.5 (Zr(NMe<sub>2</sub>)<sub>4</sub>) – 30 – 1 (H<sub>2</sub>O) – 30, and 0.5 (TMA) – 20 – 1 (H<sub>2</sub>O) – 20, respectively. ALD cycles were varied from 2, to 5, 10 and 50 in order to design different coating layer thickness on the cathode electrodes. The metal oxide ZrO<sub>2</sub> thin film was also coated on LiCoO<sub>2</sub> powder by the similar process for the comparison.

### 2.3. Characterization of the coated LiCoO<sub>2</sub> electrodes

X-Ray powder diffraction (XRD) patterns were collected on a Bruker D8 Discover Diffractometer using Co K $\alpha$  radiation ( $\lambda = 1.78897$  nm) at 40 kV and 100 mA. The morphologies and structures of various metal oxide thin film coating layers were observed by a field emission scanning electron microscope (FE-SEM, Hitachi S-4800), transmission electron microscopy (TEM, Hitachi H-7000), and high-resolution transmission electron microscope (HRTEM, JEOL 2010 FEG). The Zr and Ti K-edge X-ray absorption near edge structure (XANES) spectroscopy were obtained on the Soft X-ray Micro-characterization Beamline (SXRMB,  $\Delta E/E: \sim 10^{-4}$ ) at the Canadian Light Source (CLS), a 2.9 GeV third generation synchrotron source, using an InSb(111) and Si (111) double crystal monochromator. The Al K-edge spectra were obtained on the High Resolution Spherical Grating Monochromator (SGM). XANES were recorded in total fluorescence yield (FLY). Data were first normalized to the incident photon flux  $I_0$  measured with an ion chamber. After background correction, the XANES were then normalized using the Athena program.

### 2.4. Electrochemical testing of the coated LiCoO<sub>2</sub> electrodes

CR-2032-type coin cells were assembled in a glove box (Vacuum Atmosphere Company) under a dry argon atmosphere (moisture and oxygen level less than 1 ppm). The ALD coated electrodes and the lithium foils were used as the working electrodes and the counter electrodes, respectively. The electrolyte was composed of 1 M LiPF<sub>6</sub> salt dissolved in ethylene carbonate (EC):diethyl carbonate (DEC):ethyl methyl carbonate (EMC) of 1:1:1 volume ratio. Cyclic voltammetry and electrochemical impedance spectroscopy tests were performed on a versatile multichannel potentiostat 3/Z (VMP3). Charge–discharge characteristics were galvanostatically tested between 3.0 and 4.5 V (vs. Li/Li<sup>+</sup>) at room temperature using an Arbin BT-2000 Battery Tester. The cells were designed to measure the amount of Co dissolution into the electrolyte as below: (a) the cells were charged to 4.5 V; (b) the cells were carefully disassembled in the glove box; (c) LiCoO<sub>2</sub> electrode were stored in the electrolyte at 60 °C for 14 days; (d) the amount of Co content in the electrolyte was measured by inductively coupled plasma atomic absorption spectroscopy (ICP-AAS).


## 3. Results and discussion

Fig. 1a compares the XRD pattern of pristine LiCoO<sub>2</sub> electrode with the coated LiCoO<sub>2</sub> electrodes by TiO<sub>2</sub>, ZrO<sub>2</sub>, and Al<sub>2</sub>O<sub>3</sub>.

Obviously, in all XRD patterns, the reflection peaks originating from LiCoO<sub>2</sub> (003), (101), (006), (012), (104), (015), (009), (107), (018), (110), (113), and (021) planes marked can be observed, which shows that the coated cathode electrodes are still indexed to the pure LiCoO<sub>2</sub> with the R3m symmetry (JCPDS PDF NO. 44-145). It should be noted that due to some overlap of diffraction peaks (see Fig. S3) of the Al current collector with those of the LiCoO<sub>2</sub> cathode, some planes (such as (006), (012), (104), (009), (018), (113), and (021)) from LiCoO<sub>2</sub> show higher intensity. More importantly, the reflection peaks corresponding to LiCoO<sub>2</sub> does not alter after various metal oxide coatings, in addition, there were no new phase peaks disclosed, indicating that the ALD process has no effect on the cathode crystal structure. In this study, ALD temperatures, i.e., 85 °C, 100 °C, and 150 °C, were used to deposit the amorphous metal oxide thin films on LiCoO<sub>2</sub> cathodes. It was reported that the coating layers can react with LiCoO<sub>2</sub> at high temperature (600 °C) to form solid solutions on the surface of the cathodes [47]. But, in this study, the ALD deposition temperatures were only 150 °C at most excluding the possibility to form the solid solution on the cathodes, as demonstrated in XRD patterns. On the other hand, the absence of diffraction patterns related to TiO<sub>2</sub>, ZrO<sub>2</sub>, and Al<sub>2</sub>O<sub>3</sub> coatings is due to two facts. One is that the coating layer on the cathode electrodes exists as an amorphous phase. As we reported previously [42,48], an ALD technique is capable of tailoring the crystallinity of deposited metal oxides by controlling deposition temperature. Another fact is due to the ultra-thin nature of the coating layers on the cathode electrodes, ranging from several nanometers to sub-nanometers. Based on the ALD mechanism, the thickness of coating layers increased with number of cycles. For example, a broad pattern at around 37° was observed, corresponding to the amorphous ZrO<sub>2</sub> deposited after 100 ALD cycles (see Fig. S4 in Supplementary data).

XANES is an elemental and absorption edge specific technique that can be used as a finger print analysis. XANES analyses at the Ti, Zr, and Al K-edge were carried out to investigate the local structure of the coating layers, and they further confirmed the formation of various metal oxide layers on the electrodes. Representative spectra are shown in Fig. 1b–d for TiO<sub>2</sub>, ZrO<sub>2</sub>, and Al<sub>2</sub>O<sub>3</sub> coatings by 50 ALD cycles. The spectra of the standard TiO<sub>2</sub>, ZrO<sub>2</sub>, and Al<sub>2</sub>O<sub>3</sub> are also shown for comparison. One can observe six main features related to the standard TiO<sub>2</sub> materials in Fig. 1b due to electronic transition to unoccupied high-energy states near the Fermi level. They are sensitive to the local geometry of the probe Ti atom [49], which is in good agreement with the published data [50]. The coating layer shows the similar peaks to the standard TiO<sub>2</sub>, indicating the TiO<sub>2</sub> deposition on LiCoO<sub>2</sub> cathode by the ALD process. Similarly, in the case of the Zr and Al K-edge absorption spectra, some distinctive absorption peaks can be observed. The comparison in Fig. 1c and d also suggest the successful deposition of the ZrO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub> coating layers on LiCoO<sub>2</sub> cathode. From the above discussion, it can be concluded that various amorphous metal oxide coating layers were successfully deposited on LiCoO<sub>2</sub> cathode via an ALD process, which exhibits an advantage of precisely controlling the amorphous nature of the coating layer thickness on the cathodes by suitably adjusting ALD deposition temperatures.


In this study, commercial LiCoO<sub>2</sub> cathode with micron-size was used as the target material for coating three metal oxide coating layers via ALD with a series of cycles (2, 5, 10, and 50). The size of commercial secondary LiCoO<sub>2</sub> particle is in a range of 3–10  $\mu$ m, consisting of many primary particles with a size of 600 nm–3  $\mu$ m (see Fig. S1 in Supplementary data). Fig. 2a shows a typical high-magnification SEM image of commercial LiCoO<sub>2</sub>. Obviously, its surface is relatively smooth, being a characteristic of pristine LiCoO<sub>2</sub> particle. After an ALD process was performed on this cathode, in contrast, the surface morphology of LiCoO<sub>2</sub> cathode showed a little

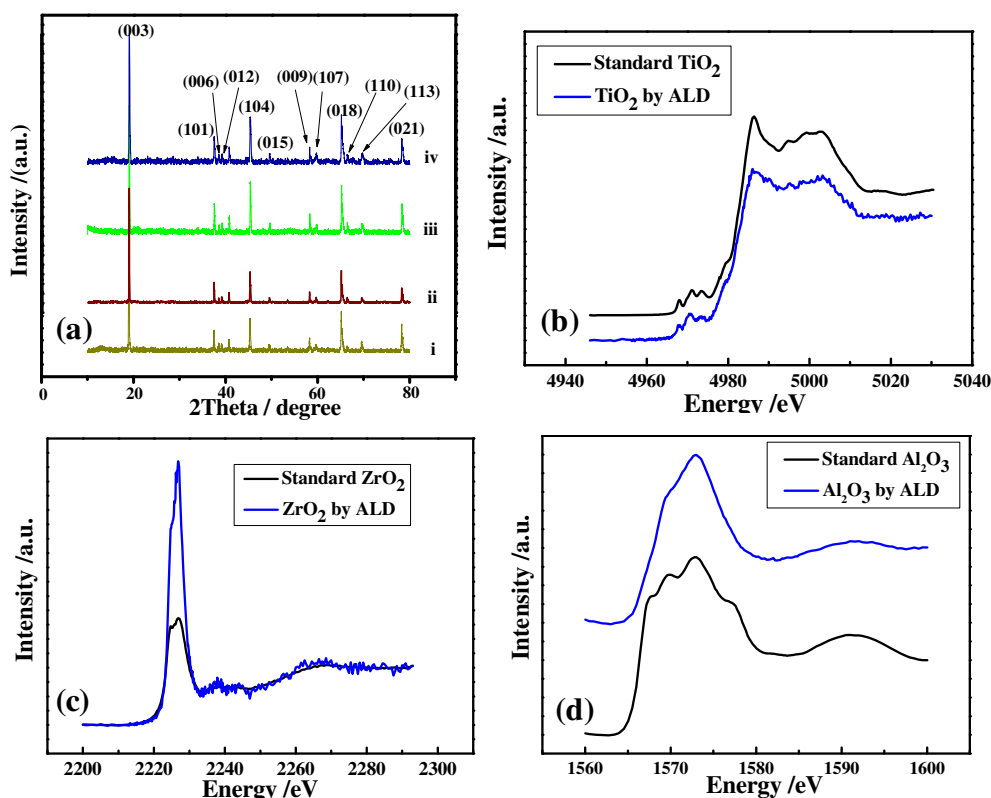

**Fig. 1.** (a) XRD patterns of (i) the pristine LiCoO<sub>2</sub> electrode and the LiCoO<sub>2</sub> electrodes coated by various metal oxides with 50 ALD cycles: (i) TiO<sub>2</sub>, (ii) ZrO<sub>2</sub>, and (iii) Al<sub>2</sub>O<sub>3</sub>; (b) Ti, (c) Zr, and (d) Al K edge structure in TiO<sub>2</sub>, ZrO<sub>2</sub>, and Al<sub>2</sub>O<sub>3</sub> coatings in LiCoO<sub>2</sub> cathode.

bit of change. As shown in Fig. 2b–i, in all the cases, an obvious coating layer can be observed on the surface of LiCoO<sub>2</sub> electrode. Additionally, the coating layers differ in their thicknesses on LiCoO<sub>2</sub> electrodes. As demonstrated in the previous research work in our


group [42], the ALD-resultant metal oxide layers increase with ALD cycles, offering the excellent advantage of precisely controlled coating layer thickness on the cathodes by adjusting ALD deposition cycles. More importantly, a very uniform and dense coating

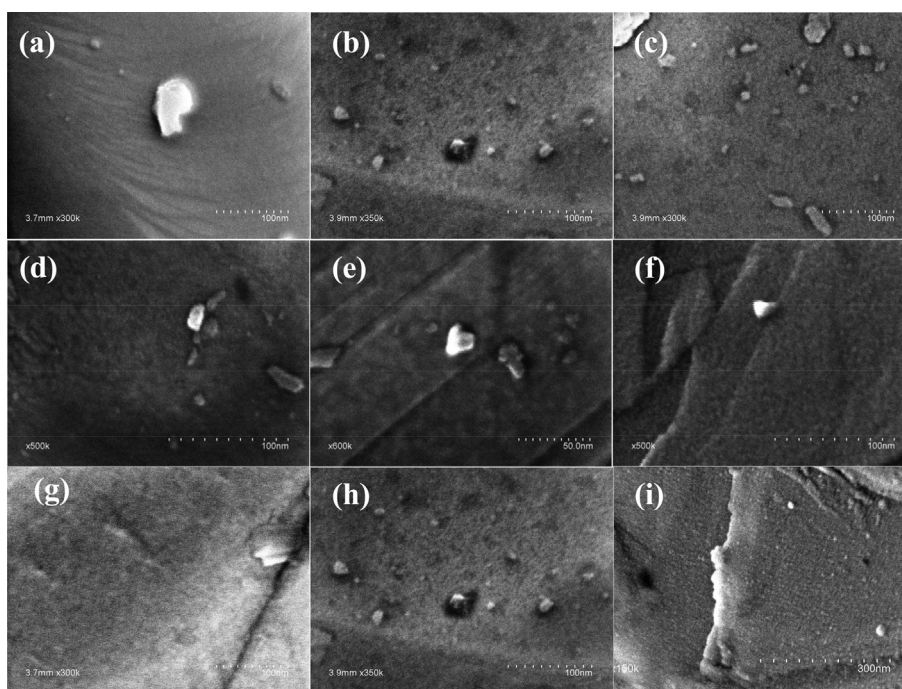

**Fig. 2.** Typical morphologies of (a) the pristine LiCoO<sub>2</sub> electrode and the LiCoO<sub>2</sub> electrodes coated by various metal oxides with different ALD cycles: (b) Al<sub>2</sub>O<sub>3</sub>-5, (c) Al<sub>2</sub>O<sub>3</sub>-10, (d) TiO<sub>2</sub>-5, (e) TiO<sub>2</sub>-10, (f) TiO<sub>2</sub>-50, (g) ZrO<sub>2</sub>-2, (h) ZrO<sub>2</sub>-5, and (i) ZrO<sub>2</sub>-50.

layer can be observed for these three metal oxides, showing another superiority in ALD-derived coating layers on the cathode electrodes. Fig. 3a–i shows elemental mapping studies on LiCoO<sub>2</sub> electrode coated by ZrO<sub>2</sub> with different ALD cycles (2, 10, and 50). The related SEM images are presented in Fig. S5 a–c in Supplementary data. It is clear that the presence of Co and O are homogenous within LiCoO<sub>2</sub> cathode, and the ZrO<sub>2</sub> coating layer is uniformly distributed on the surface of LiCoO<sub>2</sub> cathode. Similarly, ALD technique produced uniform TiO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub> coating layers on the cathode electrodes (see Fig. S6 and S7 in Supplementary data).

20 mg of the coated LiCoO<sub>2</sub> cathodes by ZrO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub> metal oxides were dissolved into a mixture solution of HNO<sub>3</sub> and HCl (v:v, 1:3) for 24 h. Obtained 1 mL solution further diluted to 9 mL DI water was measured by inductively plasma-atomic absorption spectroscopy (ICP-AAS) to determine the content of ZrO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub> metal oxides in the composite cathodes. The results are shown in Table S1. As expected, the content of both coatings in the coated cathodes increases with ALD cycles, which reveals that the thickness of the coating layers increases when ALD cycles are prolonged during the ALD process. To further quantify the amount of metal oxides deposited, we tested EDX of three metal oxides coated

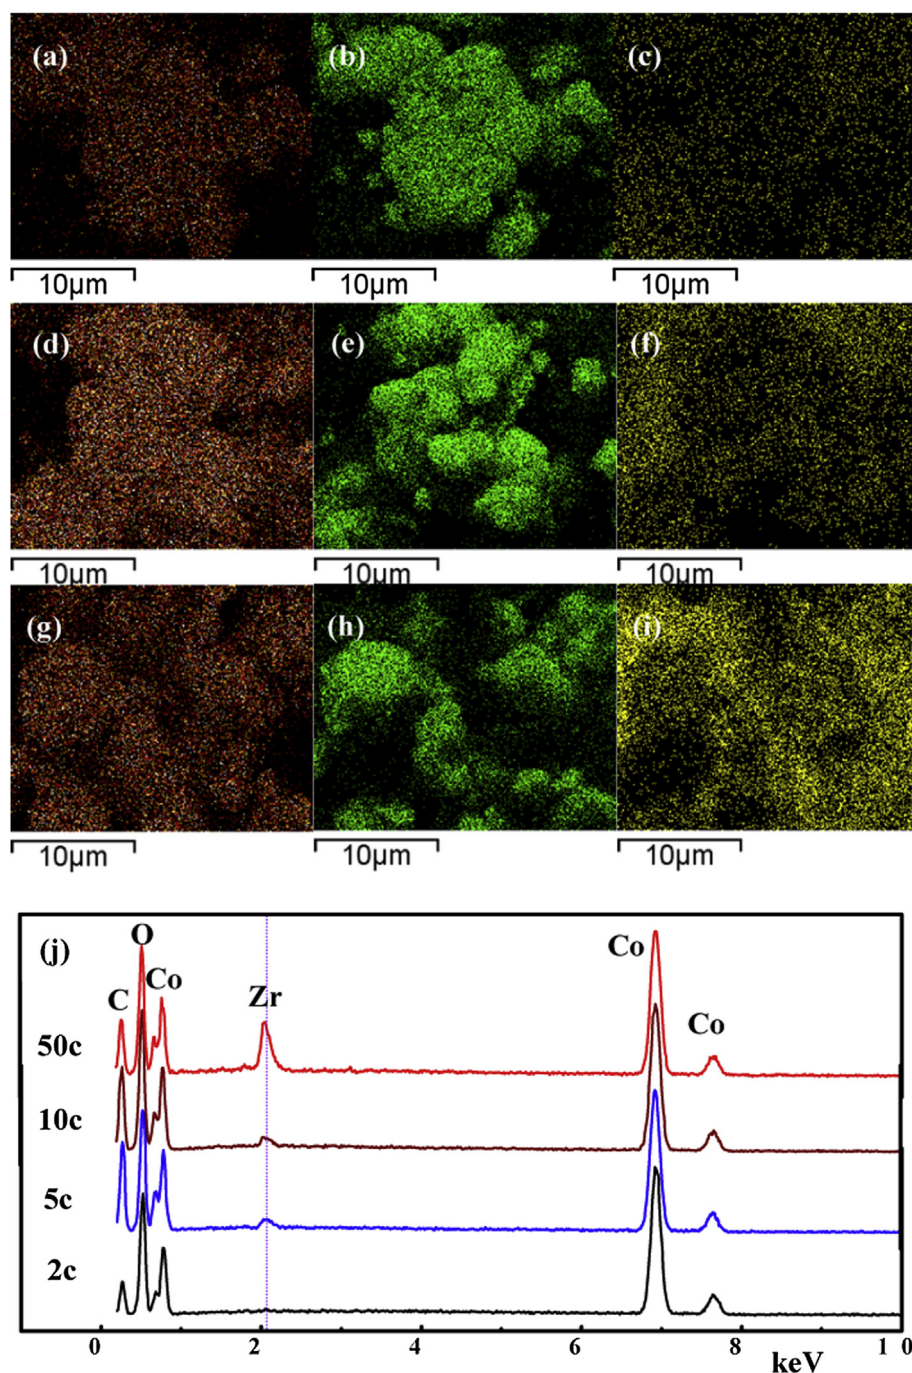


**Fig. 3.** Elemental mapping of the LiCoO<sub>2</sub> electrode coated by ZrO<sub>2</sub> with different ALD cycles: 2 (a–c), 10 (d–f), and 50 (g–i). Elemental mappings of Co (a, d, g), O (b, e, h), and Zr (c, f, i) are shown for each class. The comparison of EDX signals for different ALD coating is shown in Fig. 3j.

LiCoO<sub>2</sub> cathode, and compare the change of atomic ratio between metal (Ti, Zr, and Al) and Co with the increase of ALD cycles. In the EDX spectra in Fig. 3j and Fig. S8, the Zr, Al, Ti signals result from the metal oxide coating layers on the LiCoO<sub>2</sub> electrode. Moreover, the intensity of the peaks of Zr, Al, Ti become stronger with increased ALD cycles, in good agreement with the results of ICP-AAS. In a case of the atomic ratio of metal (Ti, Zr, and Al) and Co, the value always enhances with increased ALD cycles (see Table S2), being an obvious evidence of the thickness increase of the coating layers with ALD cycles. The thickness evolution of the ZrO<sub>2</sub> coating layers resulting from different ALD cycles was studied by the TEM technique (see Fig. S9 in Supplementary data). It is visible that the increase of the ALD cycles results in smooth and uniform coating layers with higher thickness. Clearly, it indicates the thickness evolution of the coating layers with ALD cycle: the higher the ALD cycle number, the thicker the coating layer is. Therefore, it can be concluded that the amount of metal oxides deposited increases when the ALD cycles increase.

HRTEM was performed to further confirm the coating layers on LiCoO<sub>2</sub> electrodes. From HRTEM images, it is possible to evaluate the coating layer thickness on the cathodes (see Fig. 4a–c). In a case of TiO<sub>2</sub> coating, the obtained thickness is around 5.6 nm for 50 ALD cycles based on HRTEM image of Fig. 4a. ALD rate of TTIP–H<sub>2</sub>O

system depends on a lot of deposition parameters (such as temperature, substrate type and total surface area) [51]. It was reported that when TTIP and water are employed in an ALD reaction below 200 °C, the resultant insufficient reactivity of one precursor water with TTIP could lead to deviations from the self-limited TiO<sub>2</sub> deposition from two ALD precursors. But, adsorption of TTIP on the formed TiO<sub>2</sub> surface is a self-saturated process, as a result, at low deposition temperature, the growth rate of TiO<sub>2</sub> increases as high as 1.5 Å cycle<sup>-1</sup> [51,52], which is the main reason that in this study TiO<sub>2</sub> deposition rate is beyond the typical growth (around 0.6 Å cycle<sup>-1</sup> [53]). In Fig. 4b and c, the thickness of ZrO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub> coating layers on LiCoO<sub>2</sub> cathode is 6.4 and 6.6 nm, respectively, which is in good agreement with the references [54,55]. The results in Fig. 4a–c clearly reveal that the ALD technique is capable of depositing ultra-thin metal oxide coating layers to completely cover LiCoO<sub>2</sub> cathode; moreover, the coating layer thickness can be precisely tuned by controlling ALD cycles. Al<sub>2</sub>O<sub>3</sub> was also coated on Si nanowire by the same procedure with 20 ALD cycles, and the resultant HRTEM image is shown in Fig. S10, where a 2.6 nm thickness of Al<sub>2</sub>O<sub>3</sub> layer on Si nanowire is clearly observed. The obtained thickness is comparable of one for Al<sub>2</sub>O<sub>3</sub> coated LiCoO<sub>2</sub> (6.6 nm from 50 ALD cycles), which is in good agreement with the reference [55]. This reveals that ALD mainly dominated the

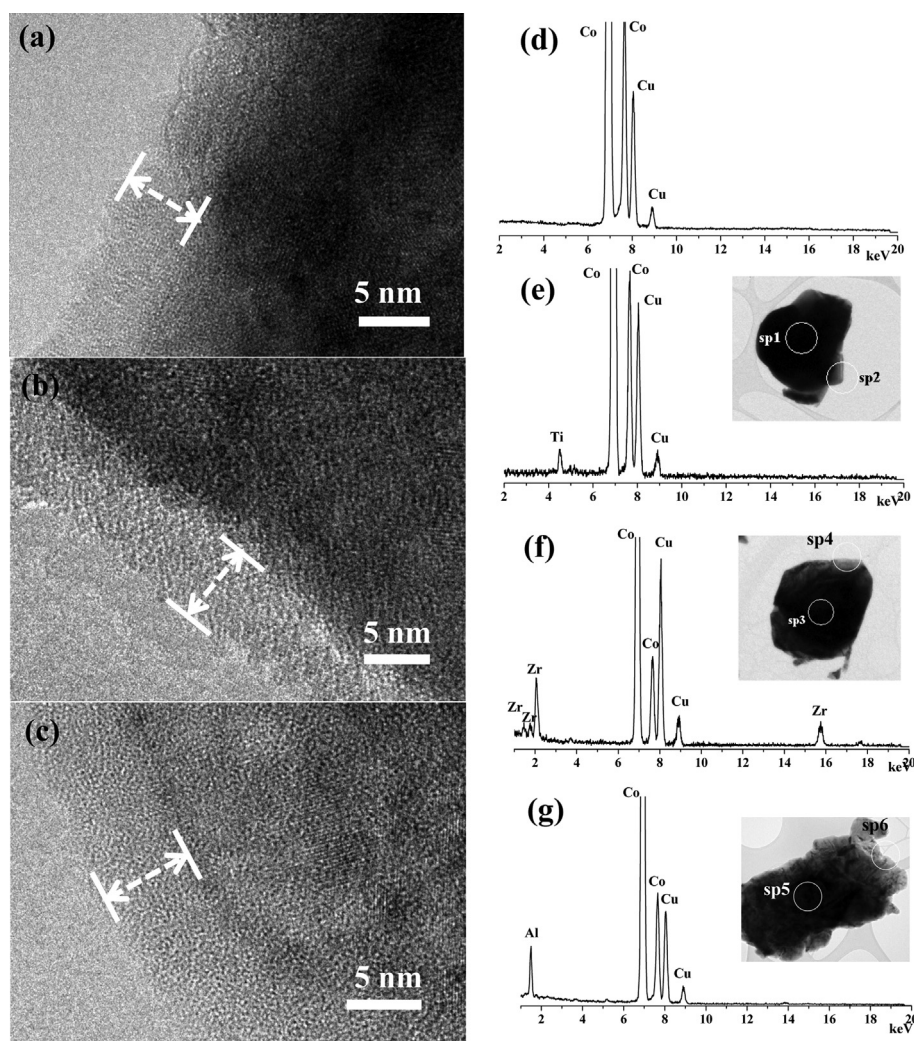

**Fig. 4.** HRTEM images of the LiCoO<sub>2</sub> cathodes by 50-ALD-cycles coating layers: (a) TiO<sub>2</sub>, (b) ZrO<sub>2</sub>, and (c) Al<sub>2</sub>O<sub>3</sub>; The EDX signals of different areas labeled as (d) sp1, sp3, sp5, (e) sp2, (f) sp4, and (g) sp6.


deposition process in our ALD chamber. High resolution EDX analysis was performed to further confirm the existence of various metal oxide coating layers on LiCoO<sub>2</sub>. The different locations labeled sp1–6 were examined to demonstrate the elemental distribution. The locations at sp1, 3, and 5 result in the similar EDX spectra as shown in Fig. 4d, where the strong Co peak is from the cathode, and the Cu signal is due to the grid of HRTEM samples. In Fig. 4e, a Ti peak exists corresponding to location sp2, which indicates a TiO<sub>2</sub> coating layer on LiCoO<sub>2</sub>. Similarly, Fig. 4f and g shows obvious evidence of other coating layer existence (say ZrO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub>).

Fig. 5a shows the typical cyclic voltammograms (CVs) obtained from pristine LiCoO<sub>2</sub> electrode at a scan rate of 0.1 mV s<sup>-1</sup> in a voltage range of 3.3–4.5 V. Clearly, there are three pairs of well defined current peaks (A/A', B/B', and C/C') corresponding to the oxidation and reduction reactions, which are positioned at (4.069/3.795 V), (4.127/4.015 V), and (4.212/4.143 V) in the first scan, respectively. The first pair of redox peaks, (4.069/3.795 V), result from the redox process of Co<sup>3+</sup> to Co<sup>4+</sup> for the first-order phase transformation (Li<sup>+</sup> extraction/insertion into LiCoO<sub>2</sub> cathode) between two hexagonal phases [56]. Another two pairs of peaks, (4.127/4.015 V), and (4.212/4.143 V), are due to the order–disorder phase transformation between hexagonal and monoclinic phases [57,58].

As shown in Fig. 10a, metal oxide coatings via ALD can be totally covered on LiCoO<sub>2</sub> powder, as a result, lithium diffusion and electron transport through the coating layers can slow down due to the poor conductivity of the metal oxides. However, if ALD process is directly applied on LiCoO<sub>2</sub> electrode, the situation is different because the metal oxides were not deposited on the contacting area between LiCoO<sub>2</sub> particles and the carbon black as the conductive agent (or the current collector). As a result, the electrically insulating coating layers do not destroy the original electrical pathways in the cathode electrodes, where the coated LiCoO<sub>2</sub> electrode still


keeps electrical conductive network among LiCoO<sub>2</sub> particles [33,59]. To compare CV curves of these two types of coatings on LiCoO<sub>2</sub> in Figs. 5b and 6e demonstrates that these two coatings can strongly affect lithium extraction from LiCoO<sub>2</sub>. By contrast, ZrO<sub>2</sub> coated LiCoO<sub>2</sub> powder shows an obvious difference during the first two charge processes, which indicates that a big irreversible process occurs in the first charge process due to ZrO<sub>2</sub> coating on LiCoO<sub>2</sub> powder. Fig. 5c compares the cycling performance of pristine LiCoO<sub>2</sub>, ZrO<sub>2</sub> coated LiCoO<sub>2</sub> powder and ZrO<sub>2</sub> coated LiCoO<sub>2</sub> electrode. Different irreversible capacity can be observed in the inset of Fig. 5c, where ZrO<sub>2</sub> coated LiCoO<sub>2</sub> powder shows higher irreversible capacity than the other two cathodes. Moreover, the three cathodes differ in their electrochemical cycling performance. The capacity loss after 100 cycles is 29%, 31%, and 19% for pristine LiCoO<sub>2</sub>, ZrO<sub>2</sub> coated LiCoO<sub>2</sub> powder and ZrO<sub>2</sub> coated LiCoO<sub>2</sub> electrode, respectively. As expected, coated LiCoO<sub>2</sub> electrode shows higher capacity retention than the pristine one. Oppositely, coated LiCoO<sub>2</sub> powder shows poorer cycling performance than the pristine one. Their rate capability is shown in Fig. 5d. During the current density increase from 100 to 700 mA g<sup>-1</sup>, the coated electrode always shows much higher energy capacities than the coated powder. As we discussed above, in the case of the coated cathode powder, ALD is capable of depositing uniform dense coating layers with poor conductivity on the cathode particles. These coatings significantly decreased lithium diffusion and electron transport in the cathode particles; as a result, it is reasonable that the coated cathode powder shows lower performance than the pristine one. From this point, we mainly focused on various metal oxide coatings on LiCoO<sub>2</sub> electrode in the following discussion.

In order to study how the various coating layers affect lithium storage of LiCoO<sub>2</sub>, the cathode electrodes coated by TiO<sub>2</sub>, ZrO<sub>2</sub>, and Al<sub>2</sub>O<sub>3</sub> were examined by cyclic voltammetry, yielding CV curves (see Fig. 6a–i). One can see that coated LiCoO<sub>2</sub> cathodes exhibit similar Li<sup>+</sup> extraction/insertion behaviors as the pristine one does.

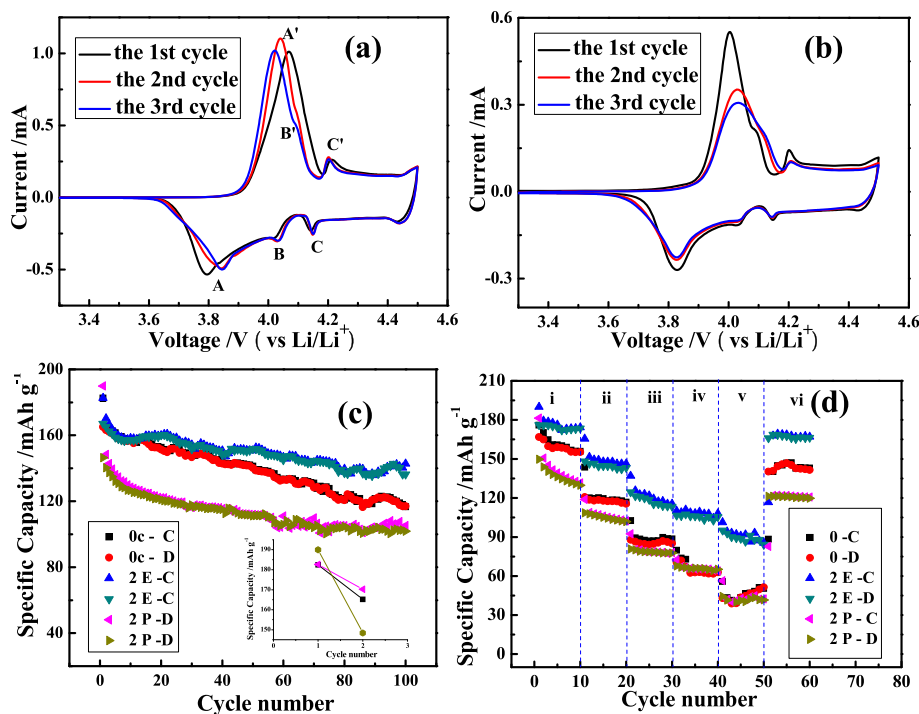

**Fig. 5.** Cyclic voltammograms of (a) the pristine LiCoO<sub>2</sub> and (b) the ZrO<sub>2</sub> coated LiCoO<sub>2</sub> powder with 2 ALD cycles (2 P); the comparison of (c) the cycling performance and (d) the rate capability ((i) 100, (ii) 300, (iii) 500, (iv) 600, (v) 700 and (vi) 100 mA g<sup>-1</sup>) for three cathodes: the pristine LiCoO<sub>2</sub>, the ZrO<sub>2</sub> coated LiCoO<sub>2</sub> powder with 2 ALD cycles, and the ZrO<sub>2</sub> coated LiCoO<sub>2</sub> electrode with 2 ALD cycles (2 E).



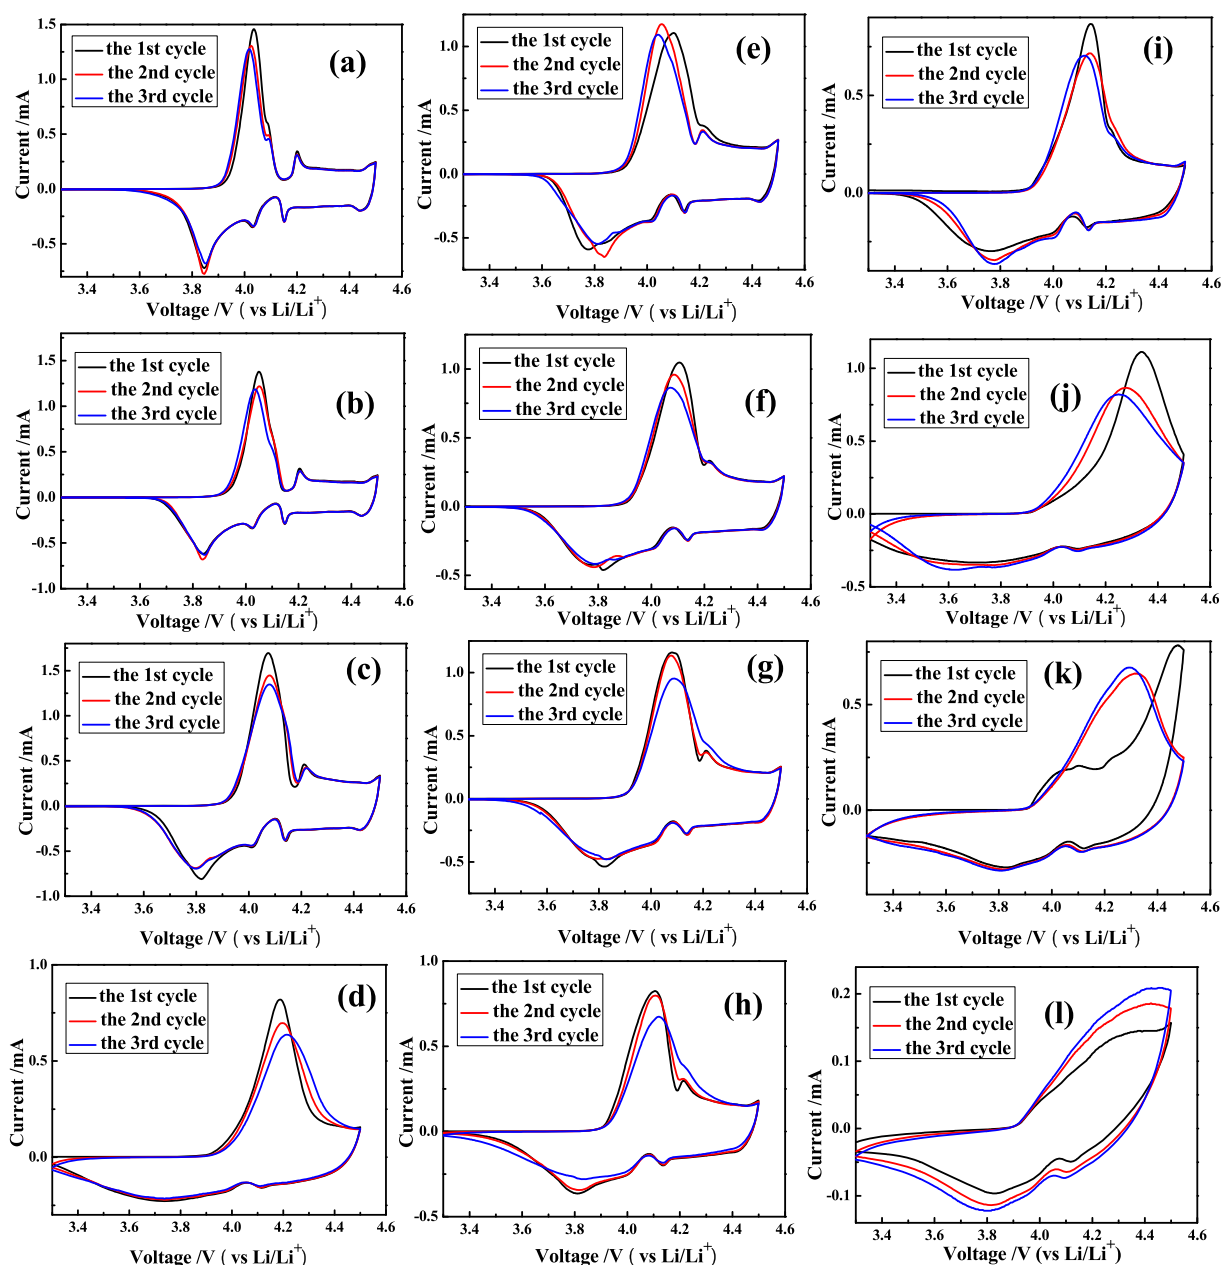

**Fig. 6.** Cyclic voltammograms of the LiCoO<sub>2</sub> electrodes coated by various metal oxides with different ALD cycles: (a) TiO<sub>2</sub>-2, (b) TiO<sub>2</sub>-5, (c) TiO<sub>2</sub>-10, (d) TiO<sub>2</sub>-50, (e) ZrO<sub>2</sub>-2, (f) ZrO<sub>2</sub>-5, (g) ZrO<sub>2</sub>-10, (h) ZrO<sub>2</sub>-50, (i) Al<sub>2</sub>O<sub>3</sub>-2, (j) Al<sub>2</sub>O<sub>3</sub>-5, (k) Al<sub>2</sub>O<sub>3</sub>-10, and (l) Al<sub>2</sub>O<sub>3</sub>-50.

However, it is clear that the oxidation and reduction peaks obviously move for ultra-thin coating layers on the electrodes, resulting in different hysteresis ( $\Delta V$ ) between the anodic and cathodic peak voltages. The detailed values were comparatively summarized in Table 1. LiCoO<sub>2</sub> cathodes coated by TiO<sub>2</sub> with 2 and 5 ALD cycles show lower  $\Delta V$  than the pristine cathode. With increasing ALD cycles, the cathodes exhibit higher  $\Delta V$ . However, ZrO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub> coatings exhibit higher  $\Delta V$  with all ALD cycles. In contrast, the  $\Delta V$  of the Al<sub>2</sub>O<sub>3</sub> coating is much higher than those of the other two. The different behaviors might stem from two aspects: different electrical conductivity and various deposition rate for coating layers on the cathode.

The cycling performance of LiCoO<sub>2</sub> electrodes with and without coating layers was studied in a voltage range of 3.3–4.5 V at a constant current density of 140 mA g<sup>-1</sup> at room temperature. Fig. 7a–c shows the cyclability of LiCoO<sub>2</sub> electrodes coated by TiO<sub>2</sub>,

ZrO<sub>2</sub>, and Al<sub>2</sub>O<sub>3</sub>, respectively. As it is shown, three types of metal oxide coatings significantly affect the energy capacities and the cycling performance of LiCoO<sub>2</sub> cathode: (1) The TiO<sub>2</sub> coating layers by 2, 5, and 10 ALD cycles could increase the specific capacities of LiCoO<sub>2</sub> electrode, while further increasing ALD cycles up to 50 worsens the cycling stability; (2) The ZrO<sub>2</sub> coating layers exhibit a bit difference with respect to the TiO<sub>2</sub> ones: 2 and 5 ALD cycle coatings produced positive effect, but negative effect from 10 to 50 ALD cycles; (3) Similar trends were observed with the Al<sub>2</sub>O<sub>3</sub> coated cathodes as the ZrO<sub>2</sub> coated ones but Al<sub>2</sub>O<sub>3</sub> coatings show better performance. Noteworthy, there was no capacity obtained from LiCoO<sub>2</sub> cathode when it was coated with a 50-ALD-cycle Al<sub>2</sub>O<sub>3</sub> film. The pristine LiCoO<sub>2</sub> cathode delivers a reversible capacity of 165.1 mAh g<sup>-1</sup> in the 100th cycle, but the capacity retention is only 70.9%. In comparison, the thinner TiO<sub>2</sub> coating layers (2, 5, and 10 ALD cycles), ZrO<sub>2</sub> coating layers (2 and 5 ALD cycles), Al<sub>2</sub>O<sub>3</sub> coating


**Table 1**

The potential of the oxidation and reduction peaks in the first three cycles for the LiCoO<sub>2</sub> electrodes coated by various metal oxides with different ALD cycles.


Coatings	ALD cycles	1st scan		2nd scan		3rd scan		Average		
		O	R	O	R	O	R	O	R	ΔV
Pristine		4.069	3.794	4.041	3.842	4.021	3.845	4.044	3.827	0.217
TiO <sub>2</sub>	2	4.035	3.845	4.025	3.846	4.017	3.852	4.025	3.848	0.178
	5	4.049	3.836	4.051	3.837	4.035	3.843	4.045	3.839	0.206
	10	4.070	3.818	4.076	3.798	4.077	3.798	4.075	3.805	0.270
	50	4.184	3.740	4.193	3.741	4.215	3.742	4.197	3.741	0.456
ZrO <sub>2</sub>	2	4.099	3.779	4.055	3.814	4.041	3.837	4.065	3.810	0.255
	5	4.105	3.825	4.085	3.822	4.072	3.819	4.087	3.822	0.265
	10	4.080	3.820	4.077	3.831	4.088	3.813	4.082	3.821	0.260
	50	4.104	3.808	4.107	3.817	4.119	3.824	4.11	3.816	0.294
Al <sub>2</sub> O <sub>3</sub>	2	4.143	3.764	4.139	3.777	4.119	3.777	4.134	3.773	0.361
	5	4.335	3.782	4.272	3.782	4.243	3.636	4.283	3.783	0.500
	10	4.475	3.836	4.323	3.820	4.294	3.814	4.364	3.823	0.541
	50	4.342	3.833	4.407	3.824	4.429	3.806	4.393	3.821	0.572

layers (2 and 5 ALD cycles) are capable of improving the cycling performance. However, any further thicker ALD coatings of the three metal oxides inhibit the cycling performance. It is worth noting that the thinnest coatings of the three metal oxides due to 2 ALD cycles commonly improve the resultant LiCoO<sub>2</sub> cathodes with the best capacity retention. Fig. 7d compares the capacity retention for these three coating layers. For Al<sub>2</sub>O<sub>3</sub> coating, the capacity fade mainly happened in the initial 10 charge/discharge cycles, while the other two coatings show the continuous capacity fade up to the 100th cycle. Obviously, the Al<sub>2</sub>O<sub>3</sub> coating layer exhibits the best capability in sustaining LiCoO<sub>2</sub> stability. After 100 charge/discharge cycles, the capacity retention of TiO<sub>2</sub>, ZrO<sub>2</sub>, and Al<sub>2</sub>O<sub>3</sub> coated LiCoO<sub>2</sub> electrodes is 81.6%, 83.5%, and 93.9%, respectively. The obtained results indicate that surface modification via ultra-thin Al<sub>2</sub>O<sub>3</sub> coating layer is an facile but effective strategy to improve the cycling stability of LiCoO<sub>2</sub> electrode under high charge cut-off voltage (3.3–4.5 V).

The RLIB rate performance is of particularly importance because the multifarious applications require high power density (high-rate capability) [60]. The rate capabilities of LiCoO<sub>2</sub> electrodes with and without coating layers are shown in Fig. 8a–c, whereby the current densities of up to 700 mA g<sup>-1</sup> have been employed. The energy capacities of the cathode electrodes gradually decrease with an increase of the current density for all samples, which results from the low diffusion rate of the lithium ions in the cathode electrodes [61,62]. It is clearly observed that these three coating layers on the cathode electrodes show different effects on the rate capability of LiCoO<sub>2</sub> cathodes. As seen in Fig. 8a–c, TiO<sub>2</sub> coatings with three ALD cycles (say 2, 5, 10) could increase the rate capability of the LiCoO<sub>2</sub> cathode. ZrO<sub>2</sub> coating by 2 ALD cycles is beneficial to enhancing its rate performance, but further thicker ALD coatings inversely decrease its rate performance. Unfortunately, different from TiO<sub>2</sub> and ZrO<sub>2</sub> coatings, Al<sub>2</sub>O<sub>3</sub> coating lacks of the ability in increasing the rate performance. The rate capability comparison of LiCoO<sub>2</sub>

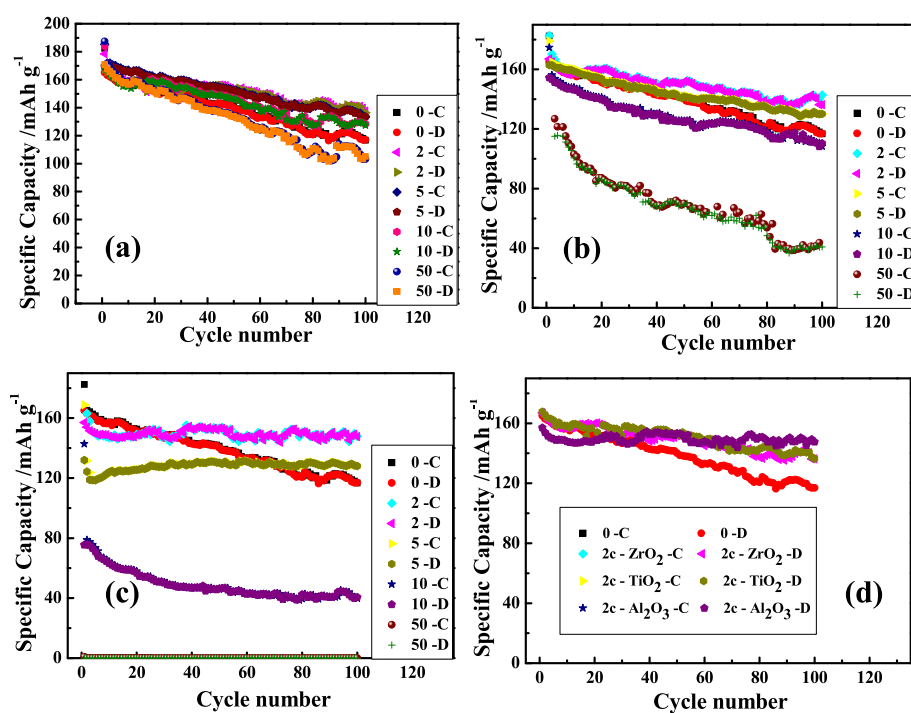

**Fig. 7.** Reversible charge/discharge capacity versus cycle numbers of the LiCoO<sub>2</sub> electrodes coated by metal oxides with different ALD cycles (0, 2, 5, 10, and 50 cycles): (a) TiO<sub>2</sub>, (b) ZrO<sub>2</sub>, and (c) Al<sub>2</sub>O<sub>3</sub>; (d) the comparison of cycling performance of LiCoO<sub>2</sub> electrodes coated by different metal oxides with 2 ALD cycles.

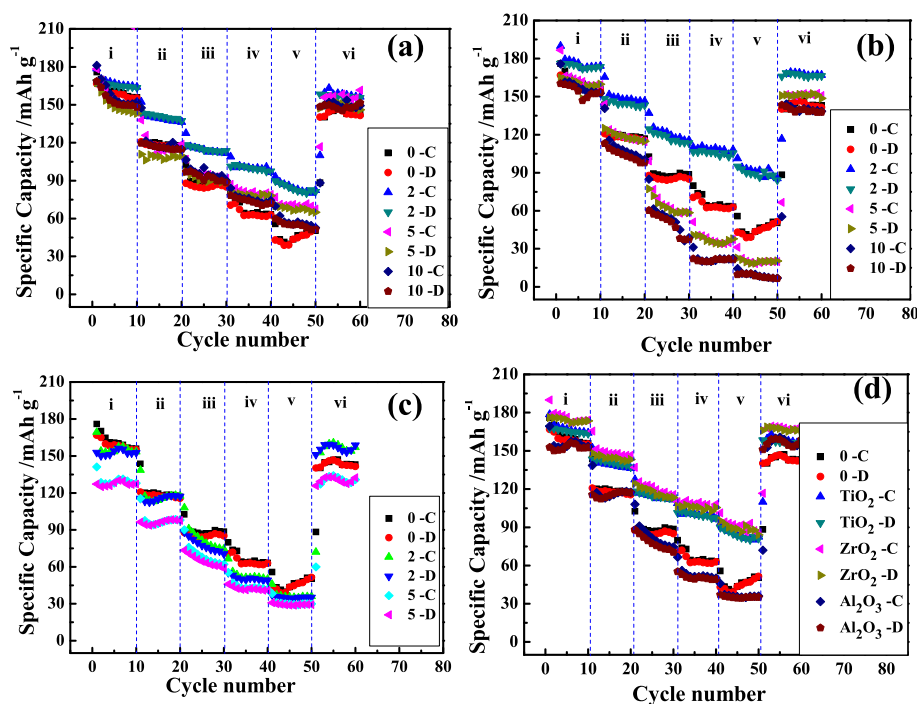


**Fig. 8.** Rate capability of LiCoO<sub>2</sub> electrodes coated by metal oxides with different ALD cycles (0, 2, 5, 10, and 50): (a) TiO<sub>2</sub>, (b) ZrO<sub>2</sub>, and (c) Al<sub>2</sub>O<sub>3</sub> at various current densities: (i) 100, (ii) 300, (iii) 500, (iv) 600, (v) 700 and (vi) 100 mA g<sup>-1</sup>; (d) the comparison of rate capability of LiCoO<sub>2</sub> electrodes coated by different metal oxides with 2 ALD cycles.

electrodes coated by different metal oxides with 2 ALD cycles is shown in Fig. 8d. Different from the result of the cycling performance in Fig. 7d, the ZrO<sub>2</sub> coating could obtain the best effect on the rate capability improvement, while the worst for the Al<sub>2</sub>O<sub>3</sub> coating. Obviously, the electrochemical performance of ALD-coated LiCoO<sub>2</sub> electrode strongly depends on the type of coating materials that the Al<sub>2</sub>O<sub>3</sub> coating shows the best cycling stability while the ZrO<sub>2</sub> coating is capable of obtaining the best rate capability. On the other hand, the ALD-coating effect on nano-sized cathodes is more distinct than that of micron-sized ones [38]. Based on obtained results, further improvement will be expected when these three coating layers are deposited onto nano-sized LiCoO<sub>2</sub>.


Different electrical conductivity of the coating layers on the cathodes inevitably affects the electrochemical impedance spectroscopy (EIS) when LiCoO<sub>2</sub> cathode reacts with lithium, which has an important impact on the battery performance. Fig. 9 shows the EIS of LiCoO<sub>2</sub> electrode as well as the influence of TiO<sub>2</sub>, ZrO<sub>2</sub>, and Al<sub>2</sub>O<sub>3</sub> coatings, respectively. All measurements were performed at 3.8 V in the discharge process at different cycles (say the 20th and 50th cycles). The obtained EIS is a collective response of kinetic processes of LiCoO<sub>2</sub> reaction with lithium, which consists of two depressed semicircles at high and medium frequency domains, and a line at low frequency region, being in good agreement with previously reported results [63,64]. As shown in Fig. 9a, the EIS of the pure electrode distinctly changes with the charge/discharge cycles, where there is a significant difference between the 20th cycle and 50th cycles. The coated electrodes show little EIS change on cycling. Importantly, it is noticeable that the EIS of Al<sub>2</sub>O<sub>3</sub> coated LiCoO<sub>2</sub> shows the nearly same trend for the 20th and 50th cycles, but its diameter of two overlapped semicircles has higher value than that of LiCoO<sub>2</sub> through these two cycles, which is due to increase of resistance by insulating Al<sub>2</sub>O<sub>3</sub> coating layer. The EIS comparison in Fig. 9 obviously shows a protective effect of the coating layers on LiCoO<sub>2</sub> electrode surface. A possible equivalent circuit is depicted in the inset of Fig. 9a to simulate LiCoO<sub>2</sub> electrode reaction with lithium, where R<sub>e</sub> is the ohmic electrolyte resistance;

R<sub>s1</sub> corresponds to the resistance for Li<sup>+</sup> migration through the surface film; C<sub>s1</sub> denotes interfacial capacitance corresponding to R<sub>s1</sub>; C<sub>dl</sub> and R<sub>ct</sub> are the double-layer capacitance and charge transfer resistance, respectively; and W is the finite-length Warburg impedance that reflects the solid-state diffusion of Li<sup>+</sup> into LiCoO<sub>2</sub> cathode [65]. As mentioned, R<sub>s1</sub> corresponds to the resistance for Li<sup>+</sup> migration through the surface film. Assuming that the surface film is related to ALD derived metal oxide layers, the pristine LiCoO<sub>2</sub> without the metal oxide layers would exhibit one semicircle in the EIS. Thus, the surface film corresponds to the solid electrolyte interphase (SEI), which is consistent with the reference [66]. To further confirm it, the EIS under open circuit condition for various cathode electrodes are shown in the inset of Fig. 9. Clearly, the EIS under open circuit condition mainly consist of one semicircle. As it is well known, the SEI could be not formed under open circuit condition. These strongly indicates that R<sub>s1</sub> corresponds to the resistance for Li<sup>+</sup> migration through the SEI. However, it can be observed that the semicircles corresponding to R<sub>s1</sub> show some difference in Fig. 9a–d. As previously reported, the SEI on the pristine LiCoO<sub>2</sub> originates from the decomposition products of the electrolyte [67]. In the case of LiCoO<sub>2</sub> coated by metal oxides, the formed SEI also consists of fluoride metals according to Eqs. (4)–(6) besides the decomposition products of the electrolyte.



Therefore, different components in the formed SEI result in some difference of the semicircles corresponding to R<sub>s1</sub>.

After simulating by the equivalent circuit in the inset of Fig. 9a, it was found that R<sub>ct</sub> of LiCoO<sub>2</sub> in the 20th cycle is 336 Ω, which is much smaller than in the 50th cycle, i.e., 505 Ω. The electrical conductivity of the coating layers is different from that of LiCoO<sub>2</sub>

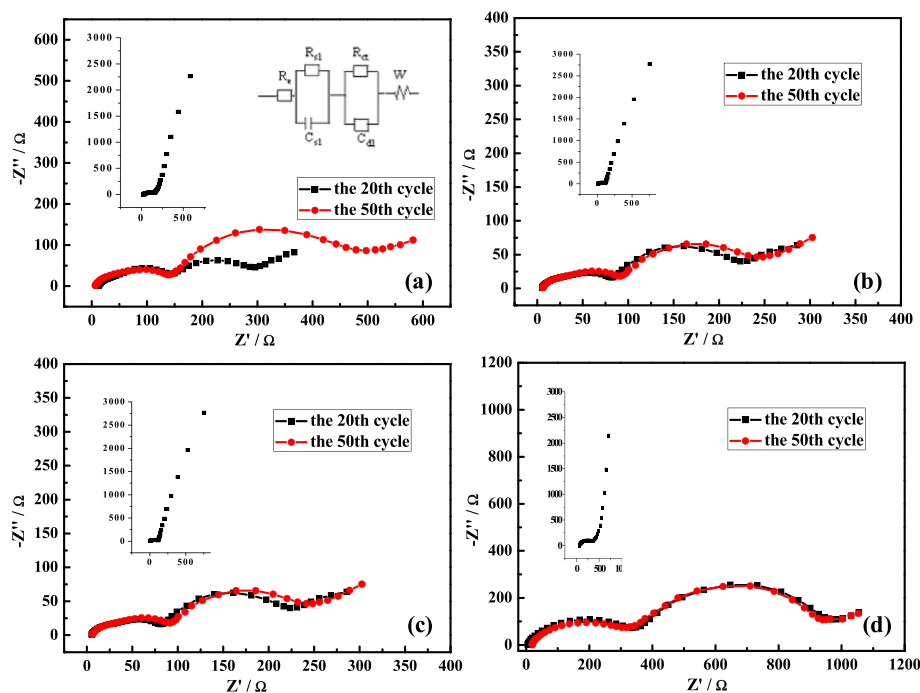


**Fig. 9.** Electrochemical impedance spectroscopy at 3.8 V in the discharge process of the 20th and 50th cycles for the LiCoO<sub>2</sub> electrodes coated by metal oxides with 10 ALD cycles: (a) the pristine LiCoO<sub>2</sub>, (b) TiO<sub>2</sub>, (c) ZrO<sub>2</sub>, and (d) Al<sub>2</sub>O<sub>3</sub>.

cathode, which significantly affects the charge transfer resistance of the cathode. As a result, TiO<sub>2</sub> coated LiCoO<sub>2</sub> shows different  $R_{ct}$  in the 20th and the 50th cycle, that is, 81  $\Omega$  and 132  $\Omega$ , respectively, while 97  $\Omega$  and 103  $\Omega$  for ZrO<sub>2</sub> coating, respectively. Interestingly, the Al<sub>2</sub>O<sub>3</sub> coating exhibits the same  $R_{ct}$  value (both are 629  $\Omega$ ) in the 20th and the 50th cycle, where high  $R_{ct}$  results from the low conductivity of Al<sub>2</sub>O<sub>3</sub> coating layer. It is obvious that during lithium insertion/extraction processes,  $R_{ct}$  of the pristine LiCoO<sub>2</sub> continually increases. In the comparison to that of the pristine LiCoO<sub>2</sub>,  $R_{ct}$  of coated LiCoO<sub>2</sub> almost keeps stable. The coating layers could reduce the decomposition of the electrolyte on the charged particle surface, moreover, upon cycling they would partially absorb the strain originating from the volumetric change of the granules, which decreases the stress among the binder, the cathode, and the conductive agent, thereby reduce the formation of the voids among them [66]. Therefore, the coating layers are capable of forming a significant protective function on LiCoO<sub>2</sub> cathodes. In particular, the Al<sub>2</sub>O<sub>3</sub> coating could protect the cathode more effectively from the reactions with the electrolyte during the charge/discharge processes.

As mentioned in the Introduction, an available approach to increase the energy capacity of LiCoO<sub>2</sub> is to charge it at higher voltages beyond 4.2 V. However, it was reported that higher voltage charging LiCoO<sub>2</sub> would undergo a severe deterioration in the cathode stability, mainly due to three aspects: (1) In the region of higher charging voltage more than 4.2 V, the amount of cobalt dissolution into the electrolyte also increases, resulting in a capacity fading occurred [68]. It is worth noting that the dissolution of LiCoO<sub>2</sub> into the electrolyte can be controlled by surface chemical reaction [69]. In this study, three types of metal oxide layers were coated on LiCoO<sub>2</sub> electrode, which can serve as an active HF scavenger to decrease the local active concentration of HF acid in the electrolyte near LiCoO<sub>2</sub> surface as Eqs. (4)–(6) [7]. As was shown in Fig. 10b, these coatings can keep LiCoO<sub>2</sub> particles from direct contact with the HF acid in the electrolyte, prevent the cobalt from dissolution in the electrolyte, thereby increase cycling performance

of LiCoO<sub>2</sub> electrode. However, the role as HF scavenger might differ among these three coatings. To confirm it, during the electrode storage at 60 °C, the amount of Co dissolution into the electrolyte was tested by ICP-AAS. The amount of pristine LiCoO<sub>2</sub> corresponds to approximately 60.3 ppm after 14 days. And the coated LiCoO<sub>2</sub> electrodes show a decrease of the Co dissolution into the electrolyte, 15.5, 14.3, and 11.6 ppm for TiO<sub>2</sub>, ZrO<sub>2</sub>, and Al<sub>2</sub>O<sub>3</sub> coatings, respectively. The Al<sub>2</sub>O<sub>3</sub> coating more significantly decreases the Co dissolution in comparison to other two coatings (see Fig. 10b). (2) As Wang et al. reported, the electrons in the conduction band of LiCoO<sub>2</sub> flows into the metal oxide coatings if the conduction band minimum of the cathode is more than those of the metal oxides, which results in the metal oxide coatings undergoing a redox reaction [37]. As a result, the electrical band structure of various metal oxides has an important influence on LiCoO<sub>2</sub> performance. In this study, the charge cut-off voltage range is 3.3–4.5 V, the metal oxide coatings on the cathode electrodes could show the band gap energy more than  $4.5 - 3.3 + 2.4 = 3.6$  eV ( $E_g$  of LiCoO<sub>2</sub> is 2.4 eV) to avoid the reduction of the metal oxide coatings [37]. The band gap energy ( $E_g$ ) of TiO<sub>2</sub>, ZrO<sub>2</sub>, and Al<sub>2</sub>O<sub>3</sub> is 3.18, 5.80, and 9.00 eV, respectively [37,70]. Therefore, the Al<sub>2</sub>O<sub>3</sub> coating provides the best cycling stability, while the worst for the TiO<sub>2</sub> coating. (3) The Co dissolution into the electrolyte is coupled with the release of lithium and oxygen with the structural degradation of LiCoO<sub>2</sub> cathode [68]. The CV curves of LiCoO<sub>2</sub> cathode could provide some information for the phase transition. As shown in Fig. 5a, an anodic peak located at 4.212 V corresponding to the hexagonal-monoclinic phase transition can be obviously observed when the cathode is charged beyond 4.2 V, which is good agreement with the references [71,72]. After coating various metal oxides by ALD, as shown in Fig. 6, the coated cathodes show different behaviors in occurring this phase transition. In Fig. 6a–d, the TiO<sub>2</sub> coating layers still show this anodic peak above 4.2 V, having no effect on this phase transition, while the decrease of the peak intensity indicates that the ZrO<sub>2</sub> coating layers can decrease this phase transition (Fig. 6e–h). Interestingly, no anodic peak above 4.2 V could be found for the

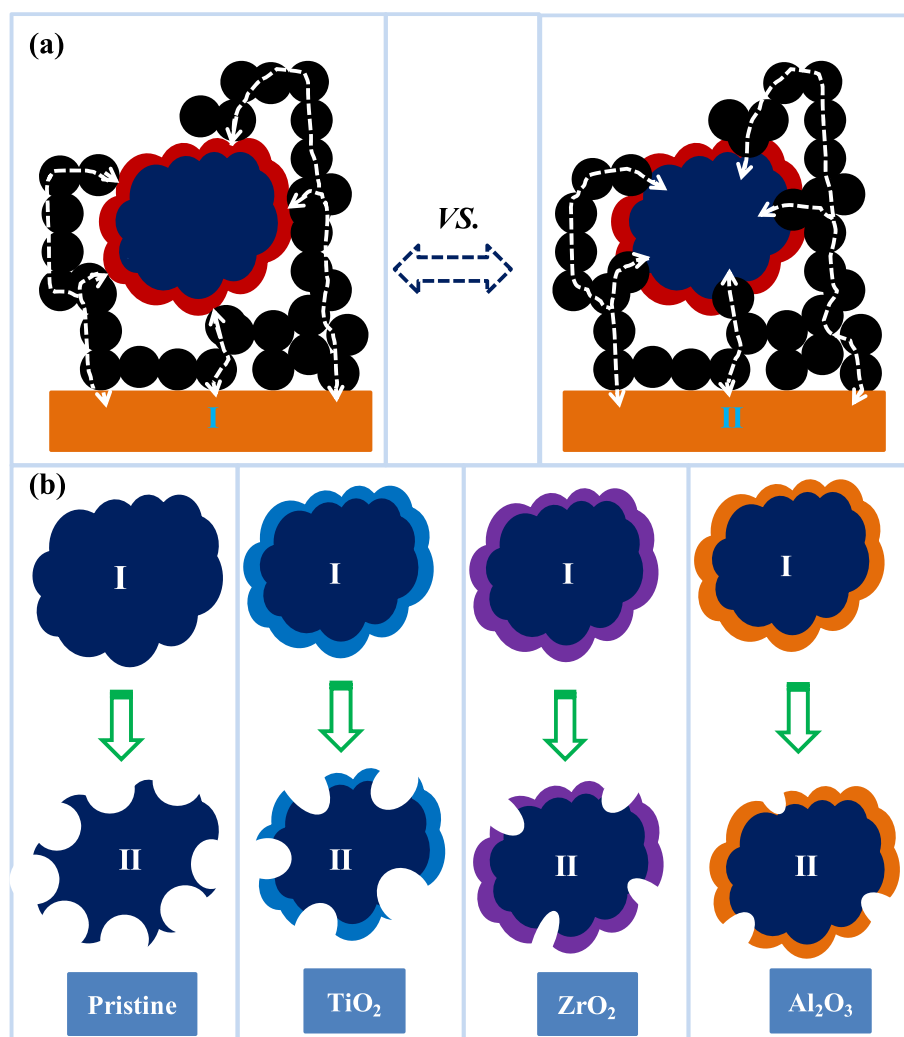

**Fig. 10.** (a) Schematic illustration of ALD coating powders (I) vs. electrodes (II) of the cathodes; (b) comparison of Co dissolution of LiCo<sub>2</sub> with various coating layers before (I) and after (II) cycles.

Al<sub>2</sub>O<sub>3</sub> coating LiCo<sub>2</sub>, which demonstrates that the Al<sub>2</sub>O<sub>3</sub> coating layers suppress this phase transition during repeated cycles. These phenomena are in good agreement with the EIS results in Fig. 9, where the suppression of the phase transition results in little change of EIS with cycle increase. (3) When the cathode Li<sub>1-x</sub>CoO<sub>2</sub> is charged up to  $x = 0.5$  (the cutoff voltage is 4.2 V), it can undergo the hexagonal-monoclinic-hexagonal phase transition accompanied by the lattice expansion ( $\sim 2.6\%$ ) in the  $c$ -direction [71–74]. Increasing the cutoff voltage up to 4.5 V, the high variation of  $c$  axis is no longer negligible that an abrupt shrinkage along the  $c$ -axis direction corresponds to  $\sim 9.0\%$  volume change, accompanying a cation disorder which causes a portion of lithium ion to enter the 3b sites of Co [75]. Moreover, the  $c$ -axis shrinkage causes some cracks within LiCo<sub>2</sub> particles as well as a loss of electrical contact between the cathodes and the conductive additives or the electrode current collector or both [48,72,76], which results in cycle degradation. The metal oxide coating layers employed have different fracture toughness resulting in various mechanical behaviors on LiCo<sub>2</sub> cathode upon repeated cycling, in the order of ZrO<sub>2</sub> > Al<sub>2</sub>O<sub>3</sub> > TiO<sub>2</sub> [77], resulting in different behavior in increasing the structural stability of LiCo<sub>2</sub> cathode. Based on above discussion, the Al<sub>2</sub>O<sub>3</sub> coating layer could show the best behavior in increasing cycling performance (at 140 mAh g<sup>-1</sup>) of LiCo<sub>2</sub> cathode. However, due to the larger electrochemical

polarization of the Al<sub>2</sub>O<sub>3</sub> coating layer, the supply of electrons becomes problematic. As a result, the Al<sub>2</sub>O<sub>3</sub> coating layer is not capable of increasing rate capability of the cathodes, oppositely, its existence as a coating layer decreases the rate capability in comparison to the pristine LiCo<sub>2</sub> cathode. In contrast, the ZrO<sub>2</sub> coating layer with higher electrical conductivity than Al<sub>2</sub>O<sub>3</sub> one could show better ability in enhancing rate capability than the other two coatings. Therefore, among three coating materials, the Al<sub>2</sub>O<sub>3</sub> coating brings the best cycling performance while the ZrO<sub>2</sub> coating contributes to the best rate capability, which reveals that ALD derived coating materials are functionally specific, and for the best improvement of a cathode, a particular coating material should be sought.

#### 4. Conclusion

In summary, ALD derived surface coatings with various metal oxides are effective to increase the cycling performance and the rate capability of the commercial LiCo<sub>2</sub> cathode in RLIBs. Our results demonstrate that various metal oxide coating layers have different influences on the cycling performance and the rate capability of LiCo<sub>2</sub> electrode: (a) different ALD-cycle deposition could cause some difference in enhancing cycling performance, and 2-ALD-cycle coatings show the best effect; (b) the Al<sub>2</sub>O<sub>3</sub> coating

with high band gap energy ( $E_g = 9.00$  eV) effectively suppresses the phase transitions during electrochemical cycling, showing better cycling performance than the  $\text{TiO}_2$  and  $\text{ZrO}_2$  ones, but the worse rate capability from its poor conductivity; (c) the  $\text{ZrO}_2$  coating by 2 ALD cycles is better in increasing the rate capability than the  $\text{TiO}_2$  and  $\text{Al}_2\text{O}_3$  ones, but further increasing ALD cycle leads to poorer rate capability in composition to the pristine  $\text{LiCoO}_2$  cathode. The various behaviors in performance improvement could be attributed to several important roles of these coating layers: (1) electrical conductivity; (2) electrical band structure; (3) suppression of the phase transition; (4) fracture toughness; and (5) scavenging HF species from the electrolyte. Therefore, this study not only demonstrates that an ALD technique is a powerful coating technique to increase the electrochemical performance of the cathodes by surface modification in RLIBs, but also shows that different metal oxide coatings have an important influence on the cathode performance in the RLIB applications. The ultra-thin  $\text{Al}_2\text{O}_3$  coating layer shows great effectiveness in enhancing cyclic performance, while  $\text{ZrO}_2$  coating layer exhibits the best effect on rate capability of  $\text{LiCoO}_2$  cathode in RLIBs.

### Acknowledgments

This research was supported by the Natural Science and Engineering Research Council of Canada (NSERC), General Motors of Canada, Canada Research Chair (CRC) Program, Canadian Foundation for Innovation (CFI), Ontario Research Fund (ORF), Early Researcher Award (ERA) and the University of Western Ontario. X. Li is grateful to Springpower International, Inc. and the MITACS Elevate Strategic Fellowship Program.

### Appendix A. Supplementary data

Supplementary data related to this article can be found at <http://dx.doi.org/10.1016/j.jpowsour.2013.08.042>.

### References

- [1] M.S. Whittingham, Chem. Rev. 104 (2004) 4271–4301.
- [2] A. Manthiram, J. Phys. Chem. Lett. 2 (2011) 176–184.
- [3] J.M. Tarascon, Philos. Trans. R. Soc. A 368 (2010) 3227–3241.
- [4] K. Mizushima, P.C. Jones, P.J. Wiseman, J.B. Goodenough, Mater. Res. Bull. 15 (1980) 783–789.
- [5] A.R. Armstrong, P.G. Bruce, Nature 381 (1996) 499–500.
- [6] X. Gu, J.L. Liu, J.H. Yang, H.J. Xiang, X.G. Gong, Y.Y. Xia, J. Phys. Chem. C 115 (2011) 12672–12676.
- [7] L. Su, Y. Jing, Z. Zhou, Nanoscale 3 (2011) 3967–3983.
- [8] M. Jo, S. Jeong, J. Cho, Electrochem. Commun. 12 (2010) 992–995.
- [9] T. Mei, K. Tang, Y. Zhu, Y. Qian, Dalton Trans. 40 (2011) 7645–7650.
- [10] H.J. Orman, P.J. Wiseman, Acta Crystallogr. Sect. C Cryst. Struct. Commun. 40 (1984) 12–14.
- [11] C. Delmas, C. Fouassier, P. Hagenmuller, Physica B+C 99 (1980) 81–85.
- [12] Y. Talyosef, B. Markovsky, R. Lavi, G. Salitra, D. Aurbach, D. Kovacheva, M. Gorova, E. Zhecheva, R. Stoyanova, J. Electrochem. Soc. 154 (2007) A682–A691.
- [13] X. Fang, Y. Lu, N. Ding, X.Y. Feng, C. Liu, C.H. Chen, Electrochim. Acta 55 (2010) 832–837.
- [14] R. Pitchai, V. Thavasi, S.G. Mhaisalkar, S. Ramakrishna, J. Mater. Chem. 21 (2011) 11040–11051.
- [15] K.F. Hsu, S.Y. Tsay, B.J. Hwang, J. Mater. Chem. 14 (2004) 2690–2695.
- [16] M. Okubo, E. Hosono, T. Kudo, H.S. Zhou, I. Honma, Solid State Ionics 180 (2009) 612–615.
- [17] X.L. Xiao, L.M. Yang, H. Zhao, Z.B. Hu, Y.D. Li, Nano Res. 5 (2012) 27–32.
- [18] D.I. Choi, G.B. Han, D.J. Lee, J.K. Park, J.W. Choi, J. Electrochem. Soc. 158 (2011) A1150–A1154.
- [19] D. Liu, G. Cao, Energy Environ. Sci. 3 (2010) 1218–1237.
- [20] M. Jo, Y.S. Hong, J. Cho, J. Electrochem. Soc. 156 (2009) A430–A434.
- [21] N. Andreu, I. Baraille, H. Martinez, R. Dedryvere, M. Loudet, D. Gonbeau, J. Phys. Chem. C 116 (2012) 20332–20341.
- [22] L. Dahéron, R. Dedryvere, H. Martinez, D. Flahaut, M. Ménétrier, C. Delmas, D. Gonbeau, Chem. Mater. 21 (2009) 5607–5616.
- [23] Y. Takahashi, S. Tode, A. Kinoshita, H. Fujimoto, I. Nakane, S. Fujitani, J. Electrochem. Soc. 155 (2008) A537–A541.
- [24] S.T. Myung, K. Amine, Y.K. Sun, J. Mater. Chem. 20 (2010) 7074–7095.
- [25] N. Pentylala, R.K. Guduru, P.S. Mohanty, Electrochim. Acta 56 (2011) 9851–9859.
- [26] R. Benedek, A. van de Walle, J. Electrochem. Soc. 155 (2008) A711–A715.
- [27] D. Aurbach, K. Gamolsky, B. Markovsky, G. Salitra, Y. Gofer, U. Heider, R. Oesten, M. Schmidt, J. Electrochem. Soc. 147 (2000) 1322–1331.
- [28] W. Hong, C. Ming-Cai, Electrochem. Solid State Lett. 9 (2006) A82–A85.
- [29] Z. Zhang, Z. Gong, Y. Yang, J. Phys. Chem. B 108 (2004) 17546–17552.
- [30] B.J. Hwang, C.Y. Chen, M.Y. Cheng, R. Santhanam, K. Ragavendran, J. Power Sources 195 (2010) 4255–4265.
- [31] L.L. Chang, Y.N. Wang, X. Zhao, J.C. Huang, Mater. Sci. Eng. A 496 (2008) 512–516.
- [32] Y. Bai, Y. Yin, N. Liu, B. Guo, H. Shi, J. Liu, Z. Wang, L. Chen, J. Power Sources 174 (2007) 328–334.
- [33] I.D. Scott, Y.S. Jung, A.S. Cavanagh, Y.F. An, A.C. Dillon, S.M. George, S.H. Lee, Nano Lett. 11 (2011) 414–418.
- [34] Z.H. Chen, Y. Qin, K. Amine, Y.K. Sun, J. Mater. Chem. 20 (2010) 7606–7612.
- [35] C. Li, H.P. Zhang, L.J. Fu, H. Liu, Y.P. Wu, E. Rahm, R. Holze, H.Q. Wu, Electrochim. Acta 51 (2006) 3872–3883.
- [36] H. Li, Z. Wang, L. Chen, X. Huang, Adv. Mater. 21 (2009) 4593–4607.
- [37] H.M. Cheng, F.M. Wang, J.P. Chu, R. Santhanam, J. Rick, S.C. Lo, J. Phys. Chem. C 116 (2012) 7629–7637.
- [38] X.N. Luan, D.S. Guan, Y. Wang, J. Nanosci. Nanotechnol. 12 (2012) 7113–7120.
- [39] J.T. Lee, F.M. Wang, C.S. Cheng, C.C. Li, C.H. Lin, Electrochim. Acta 55 (2010) 4002–4006.
- [40] Y.S. Jung, P. Lu, A.S. Cavanagh, C. Ban, G.H. Kim, S.H. Lee, S.M. George, S.J. Harris, A.C. Dillon, Adv. Energy Mater. 3 (2013) 213–219.
- [41] M. Bettge, Y. Li, B. Sankaran, N.D. Rago, T. Spila, R.T. Haasch, I. Petrov, D.P. Abraham, J. Power Sources 233 (2013) 346–357.
- [42] X. Meng, X.Q. Yang, X. Sun, Adv. Mater. 24 (2012) 3589–3615.
- [43] L.A. Riley, A.S. Cavanagh, S.M. George, Y.S. Jung, Y. Yan, S.H. Lee, A.C. Dillon, ChemPhysChem 11 (2010) 2124–2130.
- [44] X.C. Xiao, P. Lu, D. Ahn, Adv. Mater. 23 (2011) 3911–3915.
- [45] Y. He, X.Q. Yu, Y.H. Wang, H. Li, X.J. Huang, Adv. Mater. 23 (2011) 4938–4941.
- [46] Y.S. Jung, A.S. Cavanagh, L. Gedvilas, Adv. Energy Mater. 2 (2012) 1022–1027.
- [47] J. Cho, Y.J. Kim, B. Park, Chem. Mater. 12 (2000) 3788–3791.
- [48] X. Li, X. Meng, J. Liu, D. Geng, Y. Zhang, M.N. Banis, Y. Li, J. Yang, R. Li, X. Sun, M. Cai, M.W. Verbrugge, Adv. Funct. Mater. 22 (2012) 1647–1654.
- [49] H. Jung, S.M. Paek, J.B. Yoon, J.H. Choy, J. Porous Mater. 14 (2007) 369–377.
- [50] O.A. Usov, K.Y. Pogrebetskii, B.T. Melekh, Y.N. Yurev, S.A. Song, Phys. Solid State 41 (1999) 811–813.
- [51] D.M. King, X. Liang, Y. Zhou, C.S. Carney, L.F. Hakim, P. Li, A.W. Weimer, Powder Technol. 183 (2008) 356–363.
- [52] J. Aarik, A. Aidla, T. Uustare, M. Ritala, M. Leskela, Appl. Surf. Sci. 161 (2000) 385–395.
- [53] R. Katamreddy, V. Omarjee, B. Feist, C. Dussarrat, ECS Trans. 16 (2008) 113–122.
- [54] D.M. Hausmann, E. Kim, J. Becker, R.G. Gordon, Chem. Mater. 14 (2002) 4350–4358.
- [55] M.D. Groner, F.H. Fabreguette, J.W. Elam, S.M. George, Chem. Mater. 16 (2004) 639–645.
- [56] Y. Gu, D. Chen, X. Jiao, F. Liu, J. Mater. Chem. 17 (2007) 1769–1776.
- [57] K. Dokko, S. Horikoshi, T. Itoh, M. Nishizawa, M. Mohamedi, I. Uchida, J. Power Sources 90 (2000) 109–115.
- [58] J.N. Reimers, J.R. Dahn, J. Electrochem. Soc. 139 (1992) 2091–2097.
- [59] Y.S. Jung, A.S. Cavanagh, L.A. Riley, S.H. Kang, A.C. Dillon, M.D. Groner, S.M. George, S.H. Lee, Adv. Mater. 22 (2010) 2172–2176.
- [60] G. Armstrong, A.R. Armstrong, P.G. Bruce, P. Reale, B. Scrosati, Adv. Mater. 18 (2006) 2597–2600.
- [61] X. Li, Y. Xu, J. Solid State Electrochem. 12 (2008) 851–855.
- [62] X. Li, Y. Xu, Appl. Surf. Sci. 253 (2007) 8592–8596.
- [63] Y.K. Sun, J.M. Han, S.T. Myung, S.W. Lee, K. Amine, Electrochem. Commun. 8 (2006) 821–826.
- [64] X.F. Li, Y.L. Xu, Electrochem. Commun. 9 (2007) 2023–2026.
- [65] X.F. Li, A. Dhanabalan, X.B. Meng, L. Gu, X.L. Sun, C.L. Wang, Microporous Mesoporous Mater. 151 (2012) 488–494.
- [66] G. Li, Z.X. Yang, W.S. Yang, J. Power Sources 183 (2008) 741–748.
- [67] S. Malmgren, K. Cioseka, M. Hahlina, T. Gustafsson, M. Gorgoic, H. Rensmoh, K. Edström, Electrochim. Acta 97 (2013) 23–32.
- [68] G.G. Amatucci, J.M. Tarascon, L.C. Klein, Solid State Ionics 83 (1996) 167–173.
- [69] C.K. Lee, K.I. Rhee, Hydrometallurgy 68 (2003) 5–10.
- [70] V.V. Afanasev, M. Houssa, A. Stesmans, M.M. Heyns, J. Appl. Phys. 91 (2002) 3079–3084.
- [71] E. Plichta, S. Slane, M. Uchiyama, M. Salomon, D. Chua, W.B. Ebner, H.W. Lin, J. Electrochem. Soc. 136 (1989) 1865–1869.
- [72] G. Ting-Kuo Fey, C.Z. Lu, T. Prem Kumar, Y.C. Chang, Surf. Coat. Technol. 199 (2005) 22–31.
- [73] H. Wang, Y.I. Jang, B. Huang, D.R. Sadoway, Y.M. Chiang, J. Electrochem. Soc. 146 (1999) 473–480.
- [74] Z. Wang, C. Wu, L. Liu, F. Wu, L. Chen, X. Huang, J. Electrochem. Soc. 149 (2002) A466–A471.
- [75] L.J. Fu, H. Liu, C. Li, Y.P. Wu, E. Rahm, R. Holze, H.Q. Wu, Solid State Sci. 8 (2006) 113–128.
- [76] T. Fang, J.G. Duh, S.R. Sheen, Thin Solid Films 469–470 (2004) 361–365.
- [77] J. Cho, Y.J. Kim, T.J. Kim, B. Park, Angew. Chem. Int. Ed. 40 (2001) 3367–3369.